

Technical Report ARWSB-TR-17015

HIGH TEMPERATURE GRAPHENE-PEEK ADHESIVE

*Proceedings of the Society for the Advancement of Material and Process Engineering
(SAMPE) Conference
May 22-25, 2017
Seattle, Washington*

**Andrew Littlefield
Joshua A. Maurer
Stephen F. Bartolucci**

May 2017



ARMAMENT RESEARCH, DEVELOPMENT AND ENGINEERING CENTER
Weapons Software & Engineering Center
Benét Laboratories
Watervliet, NY 12189



The views, opinions, and/or findings contained in this report are those of the author(s) and should not be construed as an official Department of the Army position, policy, or decision, unless so designated by other documentation.

The citation in this report of the names of commercial firms or commercially available products or services does not constitute official endorsement by or approval of the U.S. Government.

Destroy this report when no longer needed by any method that will prevent disclosure of its contents or reconstruction of the document. Do not return to the originator.

REPORT DOCUMENTATION PAGE**Form Approved**
OMB No. 0704-0188

Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden to Washington Headquarters Service, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Reduction Project (0704-0188) Washington, DC 20503.

PLEASE DO NOT RETURN YOUR FORM TO THE ABOVE ADDRESS.**1. REPORT DATE (DD-MM-YYYY)**

May 2017

2. REPORT TYPE

Technical

3. DATES COVERED (From - To)**4. TITLE AND SUBTITLE**

HIGH TEMPERATURE GRAPHENE-PEEK ADHESIVE

5a. CONTRACT NUMBER**5b. GRANT NUMBER****5c. PROGRAM ELEMENT NUMBER****6. AUTHOR(S)**

Andrew Littlefield

Joshua A. Maurer

Stephen F. Bartolucci

5d. PROJECT NUMBER**5e. TASK NUMBER****5f. WORK UNIT NUMBER****7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES)**

U.S. Army ARDEC

Benet Laboratories, RDAR-WSB

Watervliet, NY 12189-4000

**8. PERFORMING ORGANIZATION
REPORT NUMBER**

ARWSB-TR-17015

9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES)**10. SPONSOR/MONITOR'S ACRONYM(S)****11. SPONSORING/MONITORING
AGENCY REPORT NUMBER****12. DISTRIBUTION AVAILABILITY STATEMENT**

Approved for public release; distribution is unlimited.

13. SUPPLEMENTARY NOTES

Proceedings of the Society for the Advancement of Material and Process Engineering (SAMPE) Conference

May 22-25, 2017

Seattle, Washington

14. ABSTRACT

Polyetheretherketone is a widely used engineering polymer that is especially suitable for high-temperature applications. Graphene is a two-dimensional form of carbon nanomaterial that has been studied extensively for its mechanical, electrical and thermal properties and its use as a filler in polymer matrices. Compounding graphene into polymers has the potential to improve various properties, even at very low concentrations. In this work, we have examined the incorporation of graphene nanoplatelets (GnP) and few-layer graphene into PEEK. We have fabricated composites using melt-mixing techniques, as well as by graphene functionalization and in-situ polymerization of the PEEK. In this way, we can compare the performance of the composites by two different composite fabrication methods. The composites were characterized by DSC, TGA, SEM, and mechanical properties as an adhesive in a lap-shear joint. In this work, we aim to produce a material that functions as a reusable high-temperature, thermoplastic adhesive, which can be activated by conventional heating methods, or by microwave heating. The GnPs act as microwave absorbers and heat the surrounding PEEK matrix to the point of melting, in contrast to the neat PEEK, which does not melt upon exposure to the microwaves under the same parameters. The microwave absorption properties and adhesive properties will be presented.

15. SUBJECT TERMS

Polyetheretherketone; Polymer; High-Temperature; Graphene; Carbon Nanomaterial; Graphene Nanoplatelets (GnP); PEEK

INSTRUCTIONS FOR COMPLETING SF 298

16. SECURITY CLASSIFICATION OF:			17. LIMITATION OF ABSTRACT U	18. NUMBER OF PAGES 12	19a. NAME OF RESPONSIBLE PERSON Andrew Littlefield
a. REPORT U/U	b. ABSTRACT U	c. THIS PAGE U			19b. TELEPHONE NUMBER (Include area code) (518) 266-3972

INSTRUCTIONS FOR COMPLETING SF 298

1. REPORT DATE. Full publication date, including day, month, if available. Must cite at least the year and be Year 2000 compliant, e.g., 30-06-1998; xx-08-1998; xx-xx-1998.

2. REPORT TYPE. State the type of report, such as final, technical, interim, memorandum, master's thesis, progress, quarterly, research, special, group study, etc.

3. DATES COVERED. Indicate the time during which the work was performed and the report was written, e.g., Jun 1997 - Jun 1998; 1-10 Jun 1996; May - Nov 1998; Nov 1998.

4. TITLE. Enter title and subtitle with volume number and part number, if applicable. On classified documents, enter the title classification in parentheses.

5a. CONTRACT NUMBER. Enter all contract numbers as they appear in the report, e.g. F33615-86-C-5169.

5b. GRANT NUMBER. Enter all grant numbers as they appear in the report, e.g. 1F665702D1257.

5c. PROGRAM ELEMENT NUMBER. Enter all program element numbers as they appear in the report, e.g. AFOSR-82-1234.

5d. PROJECT NUMBER. Enter all project numbers as they appear in the report, e.g. 1F665702D1257; ILIR.

5e. TASK NUMBER. Enter all task numbers as they appear in the report, e.g. 05; RF0330201; T4112.

5f. WORK UNIT NUMBER. Enter all work unit numbers as they appear in the report, e.g. 001; AFAPL30480105.

6. AUTHOR(S). Enter name(s) of person(s) responsible for writing the report, performing the research, or credited with the content of the report. The form of entry is the last name, first name, middle initial, and additional qualifiers separated by commas, e.g. Smith, Richard, Jr.

7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES). Self-explanatory.

8. PERFORMING ORGANIZATION REPORT NUMBER. Enter all unique alphanumeric report numbers assigned by the performing organization, e.g. BRL-1234; AFWL-TR-85-4017-Vol-21-PT-2.

9. SPONSORING/MONITORS AGENCY NAME(S) AND ADDRESS(ES). Enter the name and address of the organization(s) financially responsible for and monitoring the work.

10. SPONSOR/MONITOR'S ACRONYM(S). Enter, if available, e.g. BRL, ARDEC, NADC.

11. SPONSOR/MONITOR'S REPORT NUMBER(S). Enter report number as assigned by the sponsoring/ monitoring agency, if available, e.g. BRL-TR-829; -215.

12. DISTRIBUTION/AVAILABILITY STATEMENT. Use agency-mandated availability statements to indicate the public availability or distribution limitations of the report. If additional limitations/restrictions or special markings are indicated, follow agency authorization procedures, e.g. RD/FRD, PROPIN, ITAR, etc. Include copyright information.

13. SUPPLEMENTARY NOTES. Enter information not included elsewhere such as: prepared in cooperation with; translation of; report supersedes; old edition number, etc.

14. ABSTRACT. A brief (approximately 200 words) factual summary of the most significant information.

15. SUBJECT TERMS. Key words or phrases identifying major concepts in the report.

16. SECURITY CLASSIFICATION. Enter security classification in accordance with security classification regulations, e.g. U, C, S, etc. If this form contains classified information, stamp classification level on the top and bottom of this page.

17. LIMITATION OF ABSTRACT. This block must be completed to assign a distribution limitation to the abstract. Enter UU (Unclassified Unlimited) or SAR (Same as Report). An entry in this block is necessary if the abstract is to be limited.

ABSTRACT

Polyetheretherketone is a widely used engineering polymer that is especially suitable for high-temperature applications. Graphene is a two-dimensional form of carbon nanomaterial that has been studied extensively for its mechanical, electrical and thermal properties and its use as a filler in polymer matrices. Compounding graphene into polymers has the potential to improve various properties, even at very low concentrations. In this work, we have examined the incorporation of graphene nanoplatelets (GnP) and few-layer graphene into PEEK. We have fabricated composites using melt-mixing techniques, as well as by graphene functionalization and in-situ polymerization of the PEEK. In this way, we can compare the performance of the composites by two different composite fabrication methods. The composites were characterized by DSC, TGA, SEM, and mechanical properties as an adhesive in a lap-shear joint. In this work, we aim to produce a material that functions as a reusable high-temperature, thermoplastic adhesive, which can be activated by conventional heating methods, or by microwave heating. The GnPs act as microwave absorbers and heat the surrounding PEEK matrix to the point of melting, in contrast to the neat PEEK, which does not melt upon exposure to the microwaves under the same parameters. The microwave absorption properties and adhesive properties will be presented.

TABLE OF CONTENTS

Abstract	i
Table of Contents	ii
List of Figures	iii
List of Tables.....	iii
1 Introduction.....	1
2 Composite Preparation.....	2
2.1 In-Situ Polymerization of PEEK.....	2
2.1.1 Functionalization of Graphene.....	2
2.1.2 PEEK Polymerization with Functionalized and Non-Functionalized Graphene	2
3 Composite Characterization.....	3
3.1 Microstructure Analysis	3
3.2 TGA/DSC	4
3.3 Preliminary Microwave Response Characterization.....	5
3.4 Lap Shear Testing.....	6
4 Conclusions.....	8
5 Acknowledgements.....	9
6 References.....	9

LIST OF FIGURES

Figure 1. Schematic representation of the concept	1
Figure 2: a) Electron microscopy image of 1 wt% GnP dispersed in PEEK. b) Higher magnification of GnP on the surface. The layered structure of the carbon sheets is clearly seen ...	3
Figure 3: a) Electron microscopy image of 1 wt% GnP in PEEK, where the PEEK was formed by in-situ polymerization and b) 1 wt% of functionalized few-layer graphene in PEEK, where the PEEK was formed by in-situ polymerization. The PEEK polymerization is believed to start off the functional groups on the graphene, resulting in good bonding between the PEEK and graphene ..	4
Figure 4: a) Thermogravimetric analysis of polymerized PEEK with 1 wt% functionalized graphene and PEEK with 1 wt% GnP. b) Differential Scanning Calorimetry of polymerized PEEK with 1 wt% functionalized graphene and PEEK with 1 wt% GnP	5
Figure 5: 1wt% GnP-PEEK and Pure PEEK powder (white) exposed to microwaves. The GnP composite absorbs the radiation and melts, while the pure PEEK powder does not melt due to low absorption.....	6
Figure 6: Lap shear specimen in Instron.....	6
Figure 7: Lap shear specimens of pure PEEK (left) and PEEK-1wt% GnP (right) after failure.....	7
Figure 8: SEM images of the cohesive failure region with clearly visible graphene nanoplatelets shear specimens of pure PEEK (left) and PEEK-1wt% GnP (right) after failure.....	8

LIST OF TABLES

Table 1. Results of Lap Shear Testing.....	7
--	---

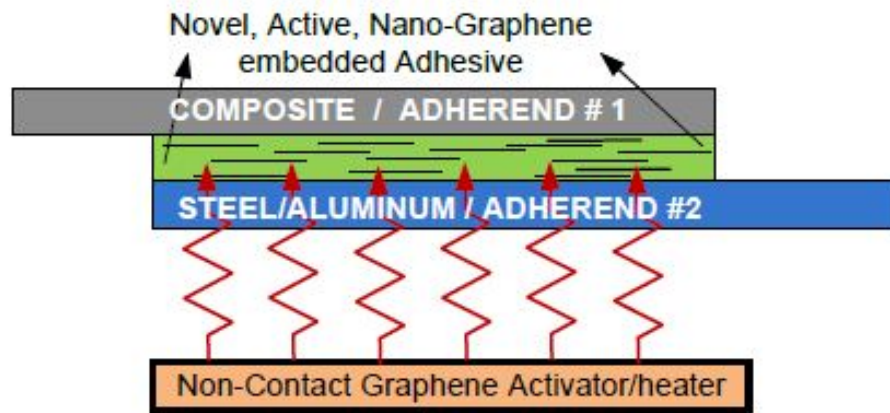


Figure 1– Schematic representation of the concept.

1 INTRODUCTION

Joining of composites can be a challenging issue. If adhesives are used, the joints are permanent and cannot be undone. If they need to be undone, inserts are often used and these inserts increase cost and weight. Additionally, fibers can be cut in the process leading to a part with weakened mechanical properties. Even with these drawbacks, most components that need to be joined are threaded together, allowing for removal of the parts at a later time. However, threaded connections are costly to design and manufacture, and are often the location of fatigue failures due to their inherent stress concentrations. From an environmental and cost standpoint, there is a large waste associated with the removal of material to form the threads, even more so in sector threads, where up to half of the machined thread is then cut away. Additionally, threaded joints often require grease to seal out environmental contamination and ensure that they can later be disassembled. This effort is aimed at replacing seldom-used threaded connections with a reusable thermoplastic adhesive.

The use of a thermoplastic makes the joining reversible, allowing any connection to be treated almost like a threaded joint, only one that uses heat instead of torque for activation. Recently, using thermoplastics as reusable adhesives has been researched by DoE for application in automobiles [1]. However, that work is focused on thermoplastics for room temperature applications, with no work being conducted on high temperature thermoplastics such as PEEK and Polyimide. The use of localized microwave radiation to heat the thermoplastic will eliminate the need for large furnaces which consume large amounts of time and energy, and ultimately heat other parts of the system that do not need to be heated. Our laboratory has begun investigating activation of high temperature thermoplastics using microwave radiation.

Figure 1 shows the basic concept. Two adherends are brought together with a graphene-doped thermoplastic between them. The assembly is then subjected to microwaves which excite the graphene nanoplatelets in the adhesive generating heat and causing the adhesive to melt. When the microwave source is removed, the adhesive solidifies joining the two materials. Since the

adhesive is a thermoplastic, subsequent applications of microwaves can be used to re-melt the adhesive and disassemble the assembly. For adherends that block microwaves, a wave guide would be needed to direct them to the bondline.

While various carbon species can absorb microwaves [2], nanospecies such as carbon nanotubes and graphene have been investigated most recently [3-5] because of their highly effective absorption at low weight loadings and ability to improve mechanical properties as well. Microwaves, when incident on an absorptive material, create heating by the interaction of the electromagnetic fields with the molecular and electronic structures of the molecules in the material exposed to the microwaves. The amount, and rate, of heating can be a function of microwave power, frequency, absorption, etc. We aim to study all these factors as we investigate microwaves as a heating source for high-temperature, reusable thermoplastic adhesives.

2 COMPOSITE PREPARATION

Melt-mixed GnP-PEEK composites, in-situ polymerized GnP-PEEK and graphene-PEEK composites have all been made. Dry powders of PEEK (Solvay Ketaspire KT-820FP, $T_m = 343\text{ }^{\circ}\text{C}$, $T_g = 143\text{ }^{\circ}\text{C}$) and 1 wt% graphene nanoplatelets (XG Sciences, Grade M) were mixed using a high speed mixer (Flacktek). GnPs are thicker (6-8 nm) than single or few-layer graphene (less than 1 nm). This uniformly mixed material was then melt compounded using a Haake torque rheometer. This is an intensive mixer with two counter rotating rotors and a temperature controlled barrel [6]. In addition to melt-mixing method, we have prepared composites using in-situ polymerization of the PEEK in the presence of GnP and few-layer graphene (functionalized and non-functionalized), which is described in more detail below. By studying various graphene species and fabrication methods, we will be able to select which method shows the best performance.

2.1 In-Situ Polymerization of PEEK

2.1.1 Functionalization of Graphene

Safety warning: The functionalization reaction makes use of an in situ diazonium salt. Diazonium salts are explosive and appropriate safety measure must be used for this reaction.

N002-PDR graphene (Angstrom Materials) with specific surface area of $600\text{ m}^2/\text{g}$ and, thus, approximately 46% surface exposed carbons atoms was used for functionalization. A round bottom flask was loaded with N002-PDR graphene (150 mg, 1eq surface) and 4-aminophenol (2.51g, 2 eq). The flask was purged with argon and anhydrous tetrahydrofuran (50 mL) was added to the flask followed by iso-phenylnitrile (3.1 mL, 2eq). The reaction was allowed to proceed at 50°C for 22 h. The functionalized graphene was collected by centrifugation and washed with hexanes and ethyl acetate.

2.1.2 PEEK Polymerization with Functionalized and Non-Functionalized Graphene

A microwave synthesis vial (30mL) was loaded with hydroquinone (1.10g, 1eq), 4,4'-difluorobenzophenone (2.18g, 1eq), sodium carbonate (1.17g, 1.1eq), and functionalized graphene or graphene nanoplatelets (30mg, 1% wt product). 1-butyl-3-methylimidazolium

bis[(trifluoromethyl)sulfonyl]amide (5 mL) was added to the vial. The vial was sealed and the reaction was carried out using a Monowave 400 microwave synthesizer (Anton Paar) at 300°C for 30 minutes using a ruby thermometer for temperature control. The resulting product was collected by centrifugation and washed by resuspension and centrifugation ten times alternating between water and acetone.

3 COMPOSITE CHARACTERIZATION

3.1 Microstructure Analysis

Electron microscopy (FEI Nanolab 600i) was performed on the samples in order to characterize the dispersion quality of the GnP and few-layer graphene in the composites. Figure 2 shows the 1 wt% GnP melt-mixed in the PEEK. Nanoplatelets are clearly seen in the fracture surface. Figure 3 shows the microstructure of PEEK-GnP (Fig. 3a) and PEEK-functionalized graphene (Fig. 3b), where the PEEK has been formed by in-situ polymerization. The PEEK is polymerized around the GnP, and it is believed to polymerize off of the functional groups in the case of the functionalized graphene. PEEK that is attached to the graphene through a functional group is expected to show improved thermal and mechanical properties, and perhaps, increased microwave absorption and heat transfer to the polymer.

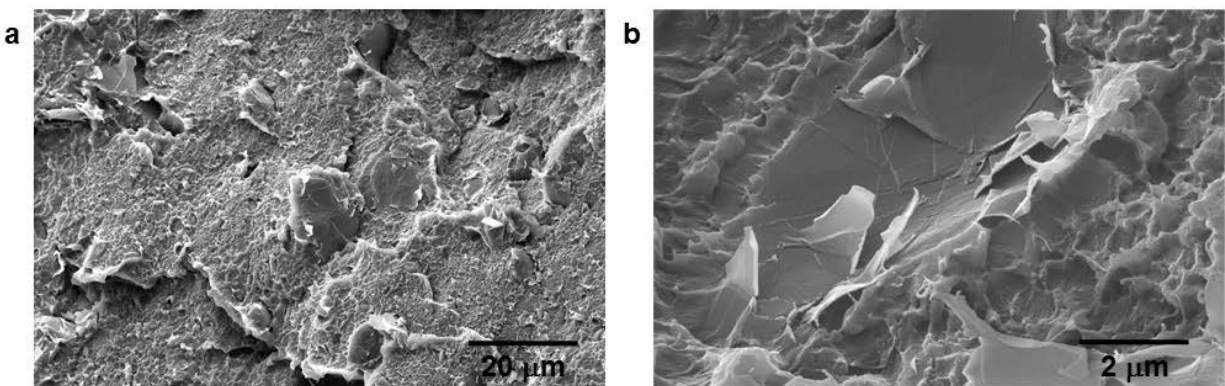


Figure 2. a) Electron microscopy image of 1 wt% GnP dispersed in PEEK. b) Higher magnification of GnP on the surface. The layered structure of the carbon sheets is clearly seen.

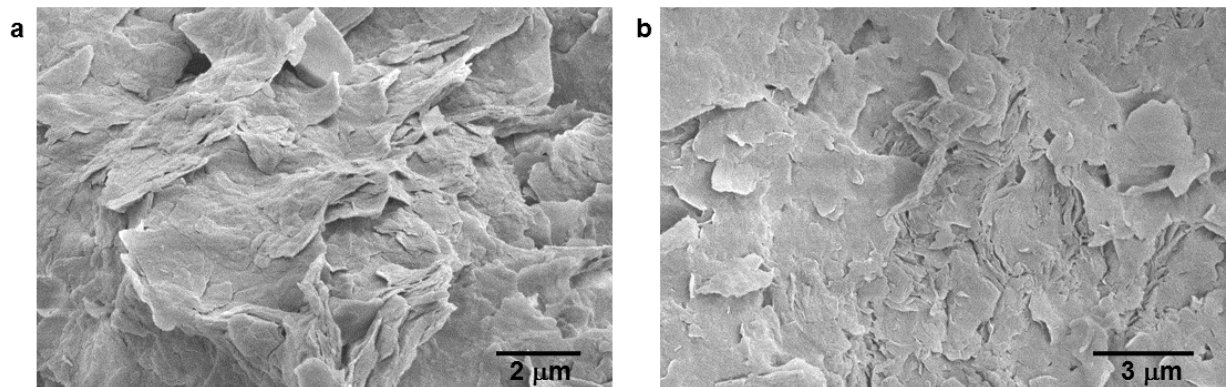


Figure 3. a) Electron microscopy image of 1 wt% GnP in PEEK, where the PEEK was formed by in-situ polymerization and b) 1 wt% of functionalized few-layer graphene in PEEK, where the PEEK was formed by in-situ polymerization. The PEEK polymerization is believed to start off the functional groups on the graphene, resulting in good bonding between the PEEK and graphene.

3.2 TGA/DSC

Thermogravimetric analysis (TGA, TA Instruments TGAQ50) and Differential Scanning Calorimetry (DSC, TA Instruments DSC Q100) of the in-situ polymerized PEEK with 1 wt% functionalized graphene and 1 wt% GnP is shown in Figure 4. Both tests were conducted in a nitrogen atmosphere and heated at 5 °C/min and cooled at 20 °C/min. The high char content (residual weight % at 1000 °C) shows that the polymerization was successful in creating high molecular weight polymer chains [7]. The results also show that the functionalized graphene adds thermal stability (TGA curve shifted to the right) to the polymer. These preliminary tests indicate that the functionalized graphene could provide improved properties to the polymer compared to the larger GnP. The cooling curves for DSC are shown in Fig. 4b. The functionalized graphene material shows a solidification exotherm at 245 °C and the GnP composite shows one at 232 °C. The GnP shows a larger crystallization exotherm at 163 °C, and the graphene composite shows little-to-no exotherm at this temperature. This could be a result of the well-dispersed, high surface area graphene interacting with the polymer chains and creating a steric hindrance effect, where the PEEK chains do not have the mobility to move and form crystallites. This could result in competing effects during microwave exposure, where high absorptivity and heat transfer may lead to faster localized melting, but lower chain mobility delays bulk melting. These factors will be studied in more depth during future work.

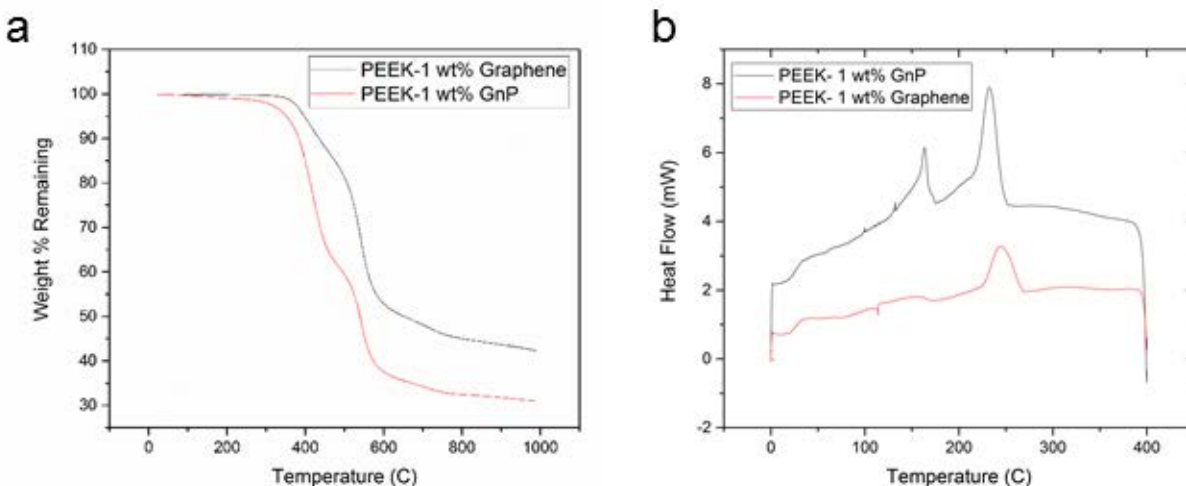


Figure 4. a) Thermogravimetric analysis of polymerized PEEK with 1 wt% functionalized graphene and PEEK with 1 wt% GnP. b) Differential Scanning Calorimetry of polymerized PEEK with 1 wt% functionalized graphene and PEEK with 1 wt% GnP.

3.3 Preliminary Microwave Response Characterization

Some preliminary tests have been conducted to observe the response of PEEK-GnP composites when exposed to microwaves.

Pure PEEK and 1 wt% GnP-PEEK was placed in a commercial microwave (1250W, 2.45 GHz) oven to see which would melt first. The 1 wt% GnP-PEEK melted after tens of minutes. The pure PEEK did not melt before the test was stopped due to the turntable rotor melting (a low temperature plastic). Fig. 5 shows 1 wt% GnP-PEEK (black, melted) and pure PEEK (white powder, no melting).

It is clear that the amount of GnP in the composite has an effect on the microwave absorption behavior. Other factors that can play a role in absorption behavior are graphene type (platelet versus mono- or few-layer), degree of dispersion, functionalization, etc. Studying these factors in PEEK nanocomposites is a current topic of research in our laboratory.

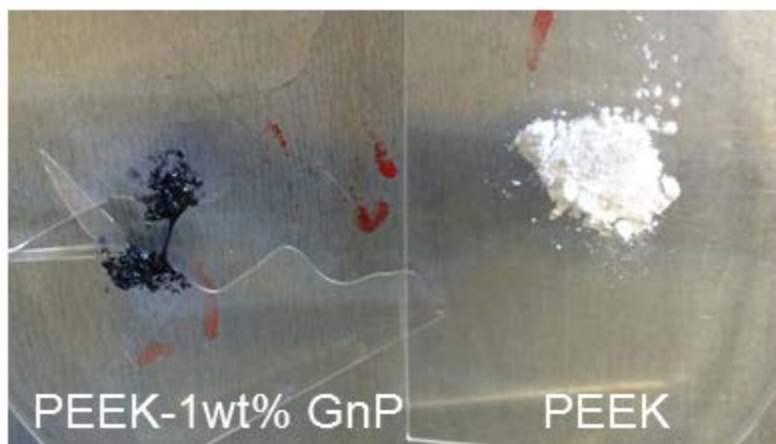


Figure 5. 1wt% GnP-PEEK and Pure PEEK powder (white) exposed to microwaves. The GnP composite absorbs the radiation and melts, while the pure PEEK powder does not melt due to low absorption.

3.4 Lap Shear Testing

A standard test for assessing the performance of an adhesive is a lap shear test. In this test two adherends are bonded together with a known overlap area and then pulled apart. We followed ASTM D1002 [8] for the testing and utilized aluminum adherends. The samples were made by taking two 203.2 mm (8 in) wide by 101.6 mm (4 in) long sheets of 2024 aluminum and overlapping them by 12.7 mm (0.5 in) in the 101.6 mm direction. In this overlap area a film of the adhesive was placed between the sheets. The assembly was then placed in platen press and heated to 357 C (675 F) at which time the pressure was increased to 2 MPa (290 psi) and then allowed to cool to room temperature. The plate was then sliced into a series of 25.4 mm (1 in) wide specimens.

A total of seven specimens using pure PEEK, 14 specimens using 1% GNP-PEEK were fabricated this way. Measurements of the individual specimen's dimensions and overlap area and thickness were taken. The specimens were then tested to failure using an Instron tensile test machine (Figure 6). Calculations were done according to ASTM D1002 to calculate failure strength. The results are given below in Table 1.



Figure 6. Lap shear specimen in Instron

Table 1 - Results of Lap Shear Testing

Material	Failure Strength	Std. Dev
PEEK	1.74 ksi	0.16 ksi
PEEK – 1 wt% GnP	1.72 ksi	0.07 ksi

Statistically, we see no difference between the 1 wt% GnP and pure PEEK. One possible reason for this is that the pure PEEK was purchased as a film whereas the 1 wt% was converted from extruded pieces to a film by repeatedly melting and compressing it on a heated platen press. This may have caused irregular dispersion of the graphene, porosity or uneven film thickness. Investigating other weight loadings of GnP, as well as few-layer graphene, could result in improved mechanical performance over the pure PEEK. There is ongoing work in our laboratory in this area.

After the test the failure mechanism of the samples was looked at. In all cases the failure was cohesive with failed adhesive being evenly split between the two adherends, Figure 7 shows a PEEK (left) and 1 wt% GnP-PEEK sample after failure. Figure 8 shows SEM images of the cohesive failure region with clearly visible graphene nanoplatelets.



Figure 7. Lap shear specimens of pure PEEK (left) and PEEK-1wt% GnP (right) after failure.

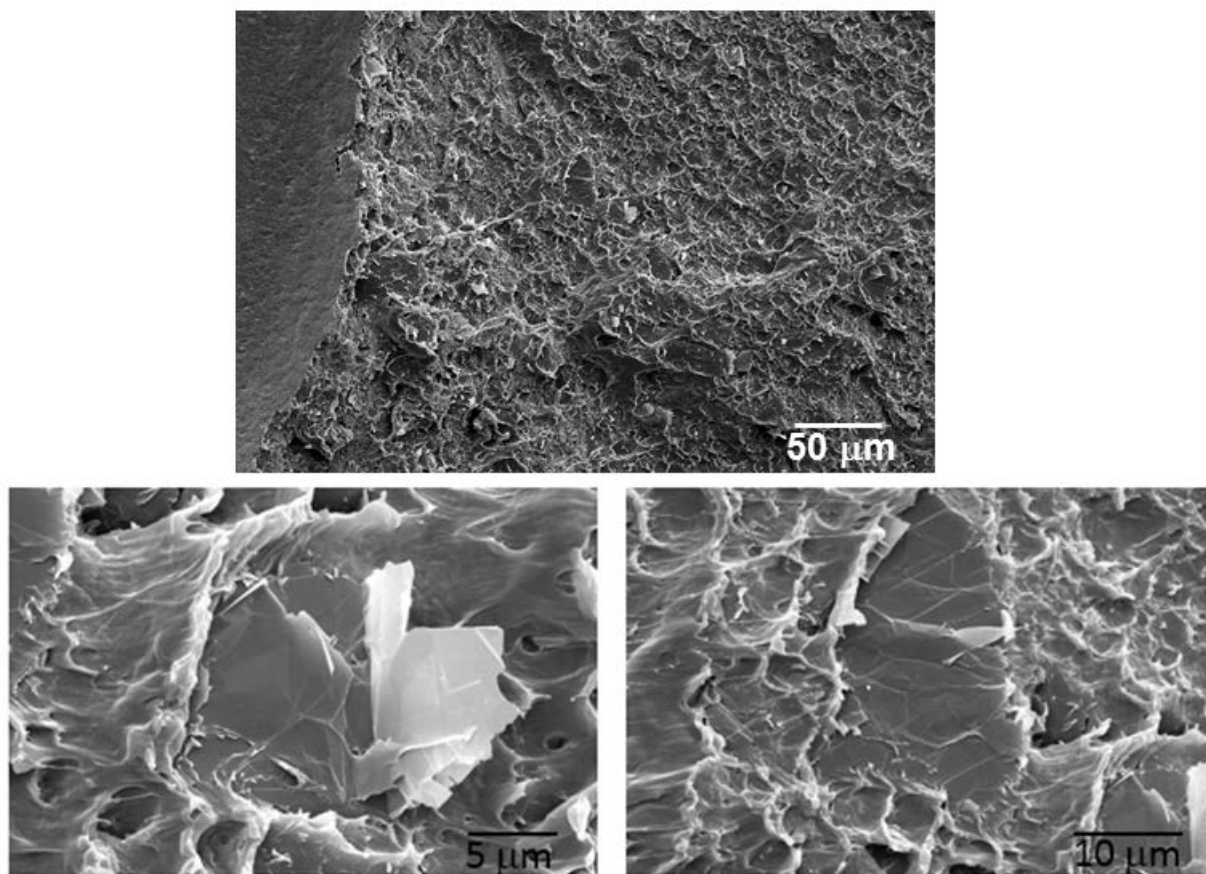


Figure 8. SEM images of the cohesive failure region with clearly visible graphene nanoplatelets.

4 CONCLUSIONS

In this study, we have examined various graphene species in PEEK as potential materials for a high-temperature adhesive. Preliminary microwave testing has shown that the graphene or graphene nanoplatelet composites can absorb microwaves to a level that will melt the PEEK, a property that could be useful in using microwaves as a localized heating source in a reusable thermoplastic adhesive application. Lap shear testing showed that the 1 wt% GnP composites had similar mechanical performance to the pure PEEK. Further optimization on these composites is needed to achieve maximum mechanical performance. We show that in-situ polymerization is a viable option for fabricating PEEK-graphene composites. Further testing of these materials is needed to demonstrate the potential as a high-temperature adhesive material.

5 ACKNOWLEDGEMENTS

The authors would like to thank Prof. Dilhan Kalyon and Dr. J. Iyer Ganapathi for their assistance in melt compounding samples at the Highly Filled Materials Institute, Stevens Institute of Technology, Hoboken, NJ.

6 REFERENCES

1. Haq M., Drzal L., “Active, Tailorable Adhesives for Dissimilar Material Bonding, Repair and Assembly,” Project ID #: LM087, Department of Energy Annual Merit Review for Vehicle Technologies Office, Washington, DC, 17 – 20 Jun 2014.
2. Qin F, Brosseau C. A review and analysis of microwave absorption in polymer composites filled with carbonaceous particles. *Journal of applied physics*. 2012 Mar 15;111(6):4.
3. Imholt TJ, Dyke CA, Hasslacher B, Pérez JM, Price DW, Roberts JA, Scott JB, Wadhawan A, Ye Z, Tour JM. Nanotubes in microwave fields: light emission, intense heat, outgassing, and reconstruction. *Chemistry of Materials*. 2003 Oct 21;15(21):3969-70.
4. Higginbotham AL, Moloney PG, Waid MC, Duque JG, Kittrell C, Schmidt HK, Stephenson JJ, Arepalli S, Yowell LL, Tour JM. Carbon nanotube composite curing through absorption of microwave radiation. *Composites Science and Technology*. 2008 Dec 31;68(15):3087-92.
5. Bai X, Zhai Y, Zhang Y. Green approach to prepare graphene-based composites with high microwave absorption capacity. *The Journal of Physical Chemistry C*. 2011 May 19;115(23):11673-7.
6. Modi SH, Dikovics KB, Gevgilili H, Mago G, Bartolucci SF, Fisher FT, Kalyon DM. Nanocomposites of poly (ether ketone) with carbon nanofibers: Effects of dispersion and thermo-oxidative degradation on development of linear viscoelasticity and crystallinity. *Polymer*. 2010 Oct 15;51(22):5236-44.
7. Jonas A, Legras R. Thermal stability and crystallization of poly (aryl ether ether ketone). *Polymer*. 1991 Jan 1;32(15):2691-706.
8. ASTM Standard D1002, 2010, "Standard Test Method for Apparent Shear Strength of Single-Lap-Joint Adhesively Bonded Metal Specimens by Tension Loading (Metal-to-Metal)," ASTM International, West Conshohocken, PA, 2003, DOI: 10.1520/D1002-10, www.astm.org